

**PrBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-y</sub>:  
SUPERCONDUCTING OR ANOMALOUSLY MAGNETIC?**

V. N. NAROZHNYI\*

*Institute for High Pressure Physics, Russian Academy of Sciences  
Troitsk, Moscow Region, 142092, Russia  
and*

*Institut für Festkörper- und Werkstofforschung  
Dresden e.V., Postfach 270016, D-01171 Dresden, Germany*

D. ECKERT, K. A. NENKOV, G. FUCHS and K.-H. MÜLLER  
*Institut für Festkörper- und Werkstofforschung  
Dresden e.V., Postfach 270016, D-01171 Dresden, Germany*

T. G. UVAROVA

*Institute of Crystallography, Russian Academy of Sciences  
Leninski pr. 59, Moscow, 117333, Russia*

Received (31 May 1999)

Revised (revised date)

In PrBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-y</sub> (Pr123) single crystals grown by the flux method the kink in the magnetic susceptibility  $\chi_{ab}(T)$ , connected with antiferromagnetic ordering of Pr, disappears after field cooling (FC) in a field  $H \parallel ab$ -plane whereas the kink in  $\chi_c(T)$  remains unchanged after FC in  $H \parallel c$ -axis. This seems to be connected with the coupling between the Pr and Cu(2) sublattices. The Curie constant  $C$  determined from the data reported for superconducting Pr123 crystals grown by the traveling-solvent floating zone (TSFZ) method (Zou *et al.*, Phys. Rev. Lett., 80, 1074 (1998)) is about one half of that for our flux-grown non-superconducting crystals. Thus, we propose that concentration of Pr in TSFZ crystals seems to be about one half of the nominal concentration for Pr123. Therefore, we propose that superconductivity in TSFZ samples is connected most probably with the partial substitution of Pr by nonmagnetic Ba.

Recently Zou *et al.*<sup>1</sup> reported the observation of bulk superconductivity (SC) for PrBa<sub>2</sub>Cu<sub>3</sub>O<sub>x</sub> (Pr123) single crystals grown by the traveling-solvent floating zone (TSFZ) method. (Earlier traces of superconductivity were found for Pr123 thin films.<sup>2</sup>) This result is in sharp contrast to earlier reports, in which it was generally accepted, that Pr123 is the only nonsuperconducting compound among the orthorhombic fully doped  $RBa_2Cu_3O_{7-y}$  ( $R=Y$ , rare earth) cuprates.<sup>3</sup>

In this work we have studied the magnetic properties of high quality Al-free orthorhombic Pr123 single crystals grown in Pt crucibles by the flux method. Atomic absorption spectroscopy analysis has shown that the Pt contamination does not exceed  $3 \cdot 10^{-3}$  at. %. X-ray analysis has revealed single phase twinned orthorhombic

---

\*Corresponding author. E-mail: narozh@ns.hppi.troitsk.ru

material with lattice parameters  $a=3.868$ ,  $b=3.911$ , and  $c=11.702$  Å.

The anisotropy of the magnetic susceptibility  $\chi$  is clearly seen in Fig. 1;  $\Delta\chi/\chi_{ab} = (\chi_c - \chi_{ab})/\chi_{ab}$  is  $\approx 10\%$  at  $T=300$  K and increases with decreasing  $T$  to  $\approx 60\%$  at  $T=15$  K (see the inset of Fig. 1A). This value is considerably larger than reported for crystals grown in alumina crucibles<sup>4</sup> ( $\approx 10\%$  at  $T=5$  K) and is close to the value reported recently for high quality Pr123 crystals grown in BaZrO<sub>3</sub> crucibles<sup>5</sup>.

We have unexpectedly discovered that the kink in  $\chi_{ab}(T)$  disappears after field cooling (FC) in a field  $H \parallel ab$ -plane, whereas the kink in  $\chi_c(T)$  remains unchanged after FC in  $H \parallel c$ -axis. A possible explanation is connected with coupling of Pr and Cu sublattices. (A theory of magnetic ordering in so called exchange-frustrated anti-ferromagnets with two spin subsystems interacting only by the anisotropic pseudo-dipole interaction has been recently proposed by S.V. Maleev.<sup>6</sup>) Pr ordering is accompanied by a counter-rotation of the ordered Cu moments in bilayer with establishing of a non-collinear Cu ordering below  $T_N$ <sup>7</sup>. In our case freezing of the Cu magnetic moments which lie in the  $ab$ -plane, by FC in  $H \parallel ab$ -plane hinders their re-orientation and, hence, the AFM ordering in the Pr sublattice<sup>8</sup>. Our results may be considered as evidence for the coupling of Pr and Cu(2) sublattices in Pr123.

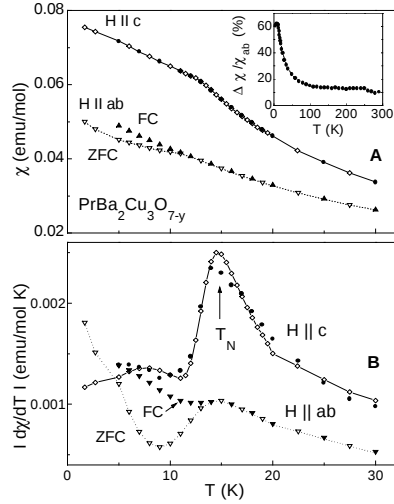


Fig. 1. (A)  $\chi$  vs  $T$  and (B)  $|d\chi(T)/dT|$  vs  $T$  for a Pr-123 single crystal. Lines connecting zero-field cooled (ZFC) data (open symbols) are guides for the eye. Solid symbols represent the FC data. The inset shows the anisotropy parameter  $(\chi_c - \chi_{ab})/\chi_{ab}$  vs  $T$ .

The values of  $\mu_{eff}=2.9 \mu_B$  and  $3.1 \mu_B$  were obtained for our crystal for  $H \parallel ab$ -plane and  $H \parallel c$ -axis, respectively. Zou *et al.*<sup>1</sup> report  $\mu_{eff}=2.92 \mu_B$ . At the same time their  $\chi(T)$  values are approximately two times lower than ours and those reported by other groups<sup>4,5</sup> for non-superconducting samples, see Fig. 2. The value of  $\mu_{eff}$  was re-estimated<sup>9</sup> directly from the data of Zou *et al.*<sup>1</sup> The estimation gives  $\mu_{eff}=2.09 \mu_B$  and the Curie constant  $C=0.546$  emu K/mol. This  $C$  value for

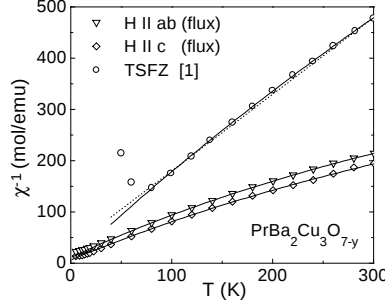


Fig. 2.  $\chi^{-1}$  vs  $T$  for flux grown and TSFZ<sup>1</sup> Pr-123 single crystals. Solid lines - fits to the Curie-Weiss law. Only some representative points are shown. For details see text.

Zou's crystal is about one half of that for our flux crystal (1.04 emu K/mol and 1.19 emu K/mol for  $H||ab$  and  $H||c$ , respectively). Based on this result, we propose that Pr occupies only about one half of the  $R$  sites (assuming for the TSFZ crystal nearly the same Pr paramagnetic local moment as for the flux grown one). We propose that the other half is occupied most probably by the nonmagnetic Ba. It should be noted, that recently SC with  $T_c \approx 97$  K was observed for  $\text{Pr}_{0.5}\text{Ca}_{0.5}\text{Ba}_2\text{Cu}_3\text{O}_{7-y}$  bulk samples prepared under high pressure<sup>10</sup>.  $\text{Ba}^{2+}$  has a larger ionic radius than  $\text{Pr}^{3+}$ , so the substitution of Ba on Pr site could give a natural explanation not only for the superconductivity in the TSFZ Pr123 but also for the elongation of distance between  $\text{CuO}_2$  planes observed by Zou *et al.*<sup>1</sup>.

### Acknowledgements

We thank S.-L. Drechsler and I. I. Mazin for useful discussions. This work was supported by DFG grant MU1015/4-1 and RFBR grant 96-02-00046G

### References

1. Z. Zou, J. Ye, K. Oka and Y. Nishihara, *Phys. Rev. Lett.* **80**, 1074 (1998).
2. H. A. Blackstead, J. D. Dow, D. B. Chriseley, J. S. Horwitz, A. Black, P. J. McGinn, A. E. Klunzinger and D. B. Pulling, *Phys. Rev.* **B54**, 6122 (1996).
3. H. B. Radousky, *J. Mater. Res.* **7**, 1917 (1992).
4. S. Uma, T. Sarkar, K. Sethupathi, M. Seshasayee, G. Rangarajan, C. Changkang, Hu Yongle, B. M. Wanklyn and J. W. Hodby, *Phys. Rev.* **B53**, 6829 (1996).
5. S. Uma, W. Schnelle, E. Gmelin, G. Rangarajan, S. Skanthakumar, J. W. Lynn, R. Walter, T. Lorenz, B. Büchner and A. Erb, *J. Phys.: Cond. Matt.* **10**, L33 (1998).
6. S. V. Maleev, *JETP Lett.* **67**, 947 (1998).
7. A. T. Boothroyd, A. Longmore, N. H. Andersen, E. Brecht and Th. Wolf, *Phys. Rev. Lett.* **78**, 130 (1997).
8. V. N. Narozhnyi, D. Eckert, K. A. Nenkov, G. Fuchs, T. G. Uvarova and K. H. Müller, *Physica* **C312**, 233 (1999).
9. V. N. Narozhnyi and S.-L. Drechsler, *Phys. Rev. Lett.* **82**, 461 (1999).
10. Y. S. Yao, Y. F. Xiong, D. Jin, J. W. Li, F. Wu, J. L. Luo and Z. X. Zhao, *Physica* **C282-287**, 49 (1999).